

PERFORMANCE CHEMICALS

Bulab[®] 600

Previous in-house testing showed that adding Bulab 600 to solvent-based epoxy coatings decreased cure time. Recent advances in analytical methods allowed for the testing of not only cure rate as a function of Bulab 600 concentration, but also cure rate as a function of concentration and temperature.

The base coating for this test is displayed in the table below. The epoxy/amine ratio was adjusted to a theoretical 1:1. Bulab 600 was post added to Part A of the formulation and the concentration range was evaluated from 0–5% at 77°F, and from 0–3% for all other temperatures studied.

| B36P292A Epoxy Formulation – Part A | | | |
|---|-----------------------|-----------------------|---------------------------------------|
| Item | Target weight (grams) | Actual weight (grams) | Calculated Epoxy Equivalents (Part A) |
| Charge the following under agitation to PT1 vessel equipped with 70 mm cowles blade | | | |
| EPOTUF [®] 38-505 | 354.10 | 354.10 | |
| DOWANOL [™] PM | 29.20 | 29.23 | |
| DOWANOL [™] DPM solvent | 29.20 | 29.20 | |
| CYMEL [®] U-21-511 | 12.70 | 12.69 | |
| Anti-Terra [®] -U | 2.70 | 2.72 | |
| Methyl isobutyl ketone (MIBK) | 36.80 | 36.82 | |
| Mix 15 min @ 630 rpm; add the following under agitation | | | |
| Busan [®] 11-M1 | 204.60 | 204.60 | |
| R5098D Copperas [®] Red Iron Oxide (Dark) | 153.50 | 153.50 | |
| BENWOOD [™] TALC 2207 | 108.00 | 108.00 | |
| WG [™] 325 muscovite mica | 35.60 | 35.60 | |
| #1 Barytes BB-2501 | 138.90 | 138.90 | |
| Hock @ 5480 rpm (20 m/s) – 4 min, then 4300 rpm 3 min, followed by 3 min @ 3390 rpm | | | |
| Mix 10 min @ 620 rpm – Stop, raise blade, scrape sides and bottom | | | |
| Hock @ 5480 rpm (20 m/s) – 4 min, then 4300 rpm 3 min, followed by 3 min @ 3390 rpm | | | |
| Check Grind – Dirty 5.5 N.S. | | | |
| Total Part A | 1105.30 | 1105.36 | 0.5058571 |

| B36P292B Epoxy Formulation Crosslinker – Part B | | | |
|---|-----------------------|-----------------------|---------------------------------------|
| Item | Target weight (grams) | Actual weight (grams) | Calculated Amine Equivalents (Part B) |
| EPOTUF 37-650 | 65.76 | 65.76 | |
| Xylene | 0.70 | 0.70 | |
| Total Part B | 66.46 | 66.46 | 0.505856 |

| | |
|--------------------------|----------------|
| Total Formulation | 1171.76 |
|--------------------------|----------------|

Epoxy cure as a function of Bulab[®] 600 addition

Initial testing showed that at 77°F gel time (indicated by the crossover point, Figure 1) and higher viscosity (Figure 2) was reached in a shorter amount of time as Bulab 600 concentration increased.

Figure 1. Loss/storage modulus curves showing gel points – 77°F


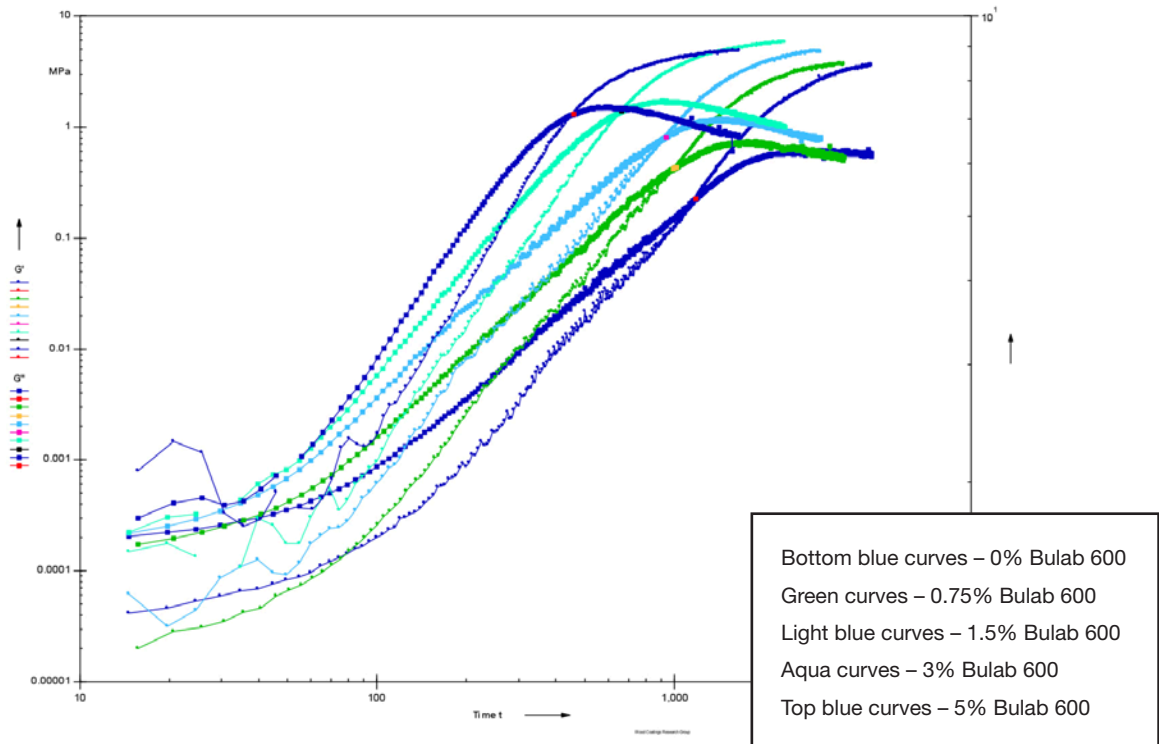


Figure 2. Complex viscosity as function of Bulab 600 – 77°F

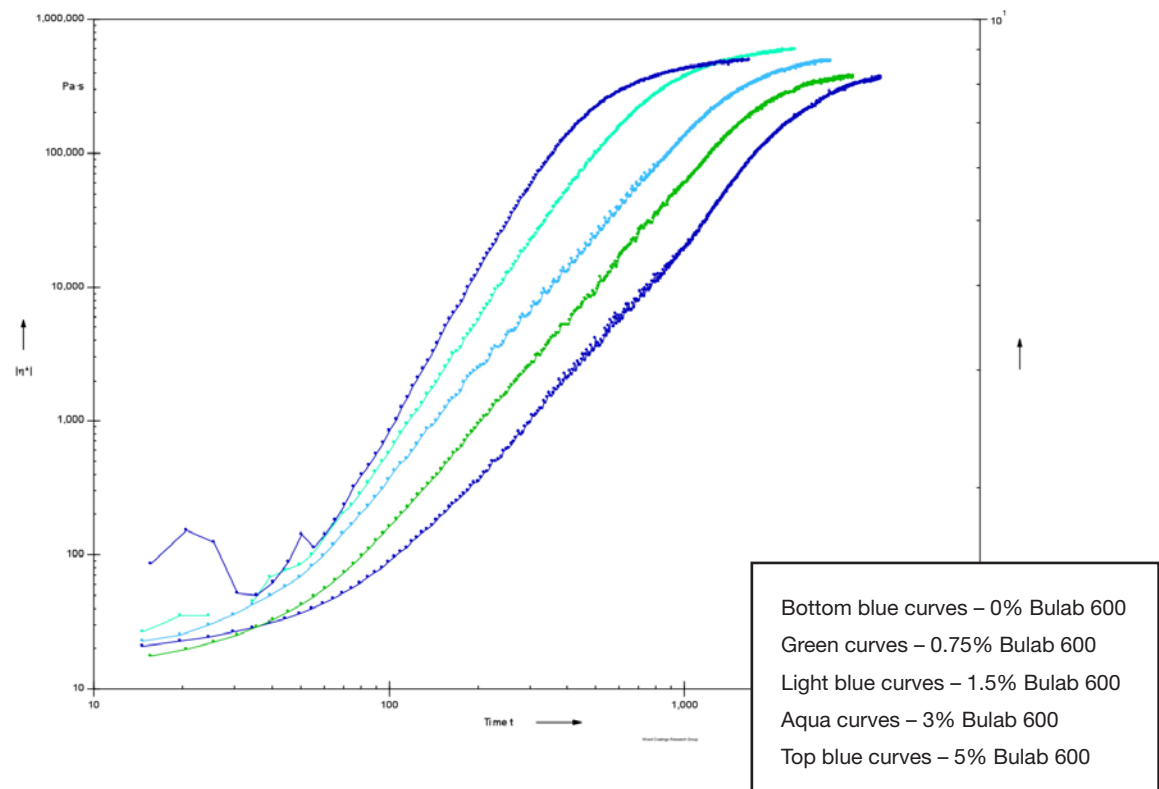

Epoxy cure as a function of Bulab® 600 addition and temperature

The study next determined that Bulab 600 increased the rate of solidification and crosslinking of the epoxy coating studied at each temperature investigated. Curing rate increased as the concentration of Bulab 600 increased, with the exception of an aberration observed at 0.75% at 50°F and 40°F relative to 0% Bulab 600 (Figures 3 and 4). As temperatures decrease from 77°F, the impact of Bulab 600 becomes greater, resulting in a reduced gel time relative to 0% Bulab 600. The 60°F curve shows the greatest slope while the 77°F curve the smallest slope (Figures 3 and 4).

Figure 3. Impact of temperature on gel time (G'/G'' crossover) as a function of Bulab 600 concentration

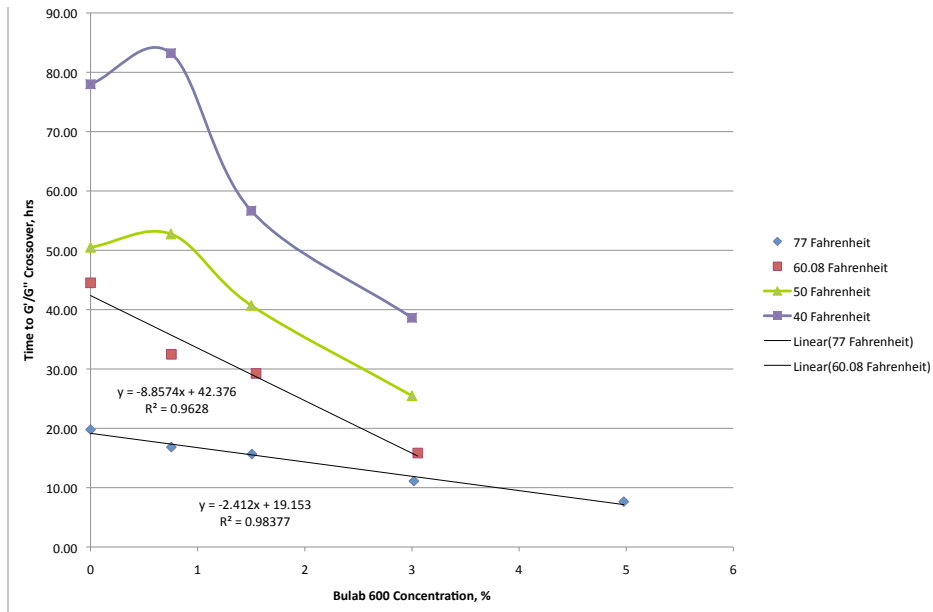


Figure 4. Impact of temperature on lineal gel time (G'/G'' crossover) as a function of Bulab 600 concentration

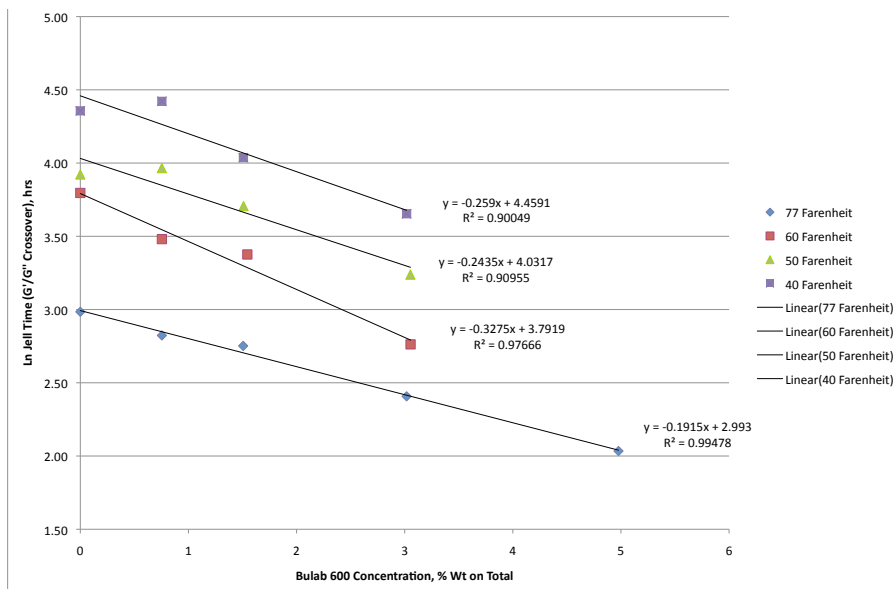


Figure 5 is an Arrhenius plot analyzing the effect of gel time as a function of temperature at a constant Bulab® 600 concentration. It is clear from the data that adding Bulab 600 dramatically improves cure of the epoxy vs. 0% Bulab 600, with 0.75% Bulab 600 showing the greatest slope for the concentrations studied.

Correlation coefficients R^2 values) are such that one may confidently predict cure-time as a function of Bulab 600 concentration and cure temperature.

Figure 5. Linear gel time vs temperature at constant Bulab 600 concentration


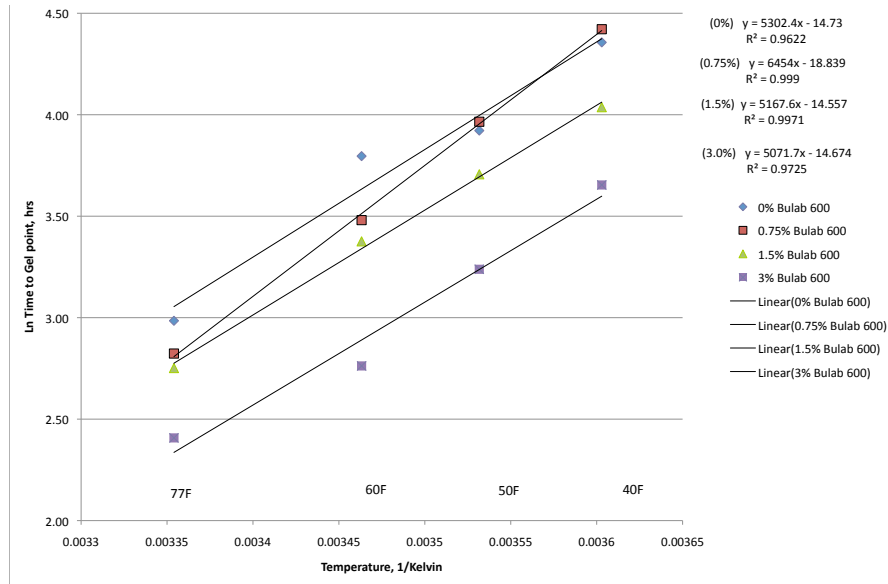


Figure 6 displays the time for the films to reach a complex viscosity of 1000 Pa·s as a function of Bulab 600 concentration and temperature. Except for the 3% Bulab concentration at 40°F, the time to reach 1000 Pa·s decreased with increasing Bulab 600 concentration at each temperature tested.

Figure 5. Impact of temperature on time Eta=1000 Pa·s as a function of Bulab 600 concentration

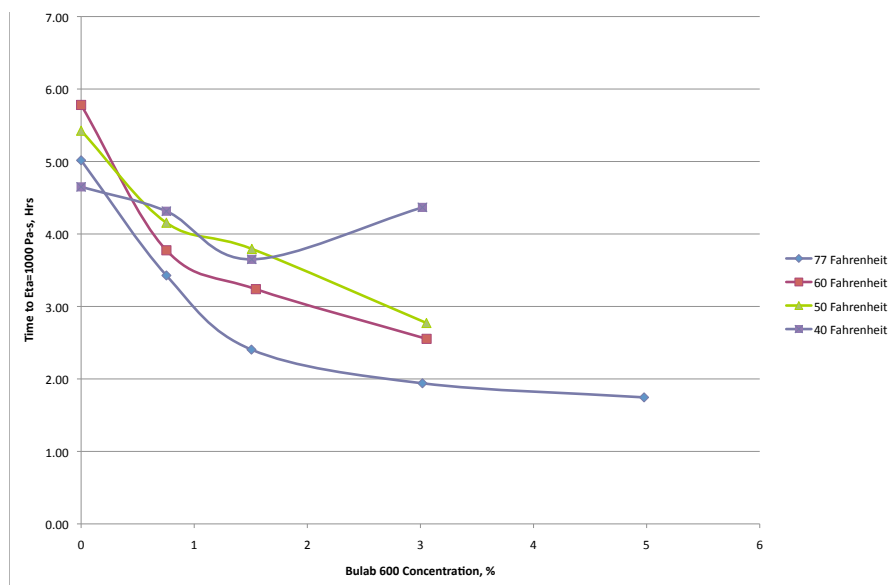

Seller warrants that this product conforms to its chemical description and is reasonably fit for the purpose referred to in the directions for use when used in accordance with the directions under normal conditions. Buyer assumes the risk of any use contrary to such directions. Seller makes no other warranty or representation of any kind, express or implied, concerning the product, including **NO IMPLIED WARRANTY OF MERCHANTABILITY OR FITNESS OF THE GOODS FOR ANY OTHER PARTICULAR PURPOSE**. No such warranties shall be implied by law and no agent of seller is authorized to alter this warranty in any way except in writing with a specific reference to this warranty. The exclusive remedy against seller shall be a claim for damages not to exceed the purchase price of the product, without regard to whether such a claim is based upon breach of warranty or tort. B312W (07/14)

Buckman in Argentina, Australia, Belgium, Brazil, Canada, Chile, China, India, Japan, Korea, Mexico, Singapore, South Africa, and USA
 Global Headquarters at 1256 N. McLean Blvd., Memphis, TN 38108, USA • Phone (901) 278-0330 / Fax (901) 276-5343 or call 1 800 BUCKMAN in the USA • knetix@buckman.com
 Canada office at 351, Joseph-Carrier, Vaudreuil-Dorion, QC J7V 5V5, Canada • Phone 1 450 424-4404 or call 1 877 282-5626 in Canada • canada@buckman.com
 Mexico office at Paseo Cuauhnáhuac Km. 13.5, 62550 Jiutepec, Morelos, México • Phone +52 777 329 3740 / Fax: +52 777 329 3741 • mexico@buckman.com